



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

## Biquadratic exchange interactions in two-dimensional magnets

**Citation for published version:**

Kartsev, A, Augustin, M, Evans, RFL, Novoselov, KS & Santos, EJG 2020, 'Biquadratic exchange interactions in two-dimensional magnets', *npj Computational Materials*, vol. 6, 150.  
<https://doi.org/10.1038/s41524-020-00416-1>

**Digital Object Identifier (DOI):**

[10.1038/s41524-020-00416-1](https://doi.org/10.1038/s41524-020-00416-1)

**Link:**

[Link to publication record in Edinburgh Research Explorer](#)

**Document Version:**

Peer reviewed version

**Published In:**

npj Computational Materials

**General rights**

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [openaccess@ed.ac.uk](mailto:openaccess@ed.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.



# Biquadratic exchange interactions in two-dimensional magnets

Alexey Kartsev<sup>1</sup>, Mathias Augustin<sup>1</sup>, Richard F. L. Evans<sup>2</sup>, Kostya S. Novoselov<sup>3,4</sup>, Elton J. G. Santos<sup>5,†</sup>

<sup>1</sup>*School of Mathematics and Physics, Queen's University Belfast, BT7 1NN, United Kingdom*

<sup>2</sup>*Department of Physics, The University of York, York, YO10 5DD, UK*

<sup>3</sup>*Department of Material Science & Engineering, National University of Singapore, Block EA, 9 Engineering Drive 1, 117575, Singapore*

<sup>4</sup>*Chongqing 2D Materials Institute, Liangjiang New Area, Chongqing 400714, China*

<sup>5</sup>*Institute for Condensed Matter Physics and Complex Systems, School of Physics and Astronomy, The University of Edinburgh, EH9 3FD, UK.*

<sup>†</sup>*Corresponding author: esantos@ed.ac.uk*

Magnetism in recently discovered van der Waals materials has opened several avenues in the study of fundamental spin interactions in truly two-dimensions. A paramount question is what effect higher-order interactions beyond bilinear Heisenberg exchange have on the magnetic properties of few-atom thick compounds. Here we demonstrate that biquadratic exchange interactions, which is the simplest and most natural form of non-Heisenberg coupling, assume a key role in the magnetic properties of layered magnets. Using a combination of nonperturbative analytical techniques, non-collinear first-principles methods and classical Monte Carlo calculations that incorporate higher-order exchange, we show that several quantities including magnetic anisotropies, spin-wave gaps and topological spin-excitations are intrinsically renormalized leading to further thermal stability of the layers. We develop a spin Hamiltonian that also contains antisymmetric exchanges (e.g. Dzyaloshinskii–Moriya interactions) to successfully rationalize numerous observations, such as the non-Ising character of several compounds despite a strong magnetic anisotropy, peculiarities of the magnon spectrum of 2D magnets, and the discrepancy between measured and calculated Curie temperatures. Our results provide a theoretical framework for the exploration of different physical phenomena in 2D magnets where biquadratic exchange interactions have an important contribution.

**Keywords:** 2D magnets, higher order exchange interactions, Monte Carlo, biquadratic exchange, ferromagnetism, two-dimensional materials, topological magnons, magnon spectra

## 32 Introduction

33 The finding of magnetism in atomically thin van der Waals (vdW) materials<sup>1,2</sup> has attracted an  
34 increasing amount of interest in the investigation of magnetic phenomena at the nanoscale<sup>3</sup>. Im-  
35 portant in the understanding and applications of 2D vdW magnets in real technologies is the eluci-  
36 dation of fundamental interactions that determine their magnetic properties, such as the exchange  
37 interactions between the spins. These interactions govern the magnetic ordering and can be ei-  
38 ther symmetric, which determine collinear ferromagnets and anti-ferromagnets, or antisymmetric,  
39 which promote topological non-trivial spin textures, e.g. skyrmions. Higher-order exchange terms  
40 involving the hopping of two or more electrons play a pivotal role in the spin-ordering of low-  
41 dimensional nanostructures. For instance, biquadratic (BQ) exchange interactions are critical in the  
42 elucidation of the magnetic features of several systems, such as multilayer materials<sup>4</sup>, perovskites<sup>5</sup>,  
43 iron-based superconductors<sup>6,7</sup>, iron tellurides<sup>8</sup> and oxides<sup>9</sup>. Indeed, in materials where the ex-  
44 change is for some reason weak<sup>10</sup> (e.g. low-temperature magnets) BQ exchange has a particularly  
45 strong influence being the case of several 2D magnets discovered so far<sup>11,12</sup>.

46 Here we identify that several families of 2D magnets including metals, insulators and small  
47 band gap semiconductors, develop substantially large BQ exchange interactions. The delicate  
48 interplay between the superexchange process through the non-magnetic atom and the Coulomb  
49 repulsion at neighboring spin-sites involving more than one electron induces sizable corrections to  
50 the total energy of the systems beyond bilinear spin models, e.g. Kitaev, Heisenberg, Ising. We  
51 developed a generalized non-Heisenberg spin Hamiltonian that includes both BQ and Dzyaloshin-

skii–Moriya interactions (DMI), providing a universal picture of the spin properties of 2D vdW magnets. We show that while BQ exchange interactions give substantial contributions to the thermal properties, such as in critical temperatures ( $T_c$ ), non-collinear spin effects via DMI are negligible. The model also offers insights via analytical equations into the spin excitations of 2D materials as a general formalism is developed for materials that hold honeycomb crystal structure, ferromagnetism and out-of-plane easy axis in a universal basis. Our results provide the conceptual framework to understand a variety of 2D magnetic materials in a consistent way explaining numerous experimental observations, including controversies on the magnetic properties of  $\text{CrI}_3$  or  $\text{CrBr}_3$ .

## Results

**Biquadratic exchange interactions** In order to calculate the different exchange contributions to the total energy at the level of first-principles methods (see Supplementary Sections 1-4 for details), we map the angular dependence of the spins  $\mathbf{S}_j = \mu_s \mathbf{s}_j$ , where  $\mu_s$  is the magnetic moment and  $|\mathbf{s}_j| = 1$ , in the unit cell of the layered material<sup>5,13,14</sup> (Fig. 1a). We rotate the spins by  $\theta$  between two known spin configurations: from ferromagnetic (FM) at  $\theta = 0$ , to anti-ferromagnetic (AFM) at  $\theta = 180^\circ$ . Small steps in  $\theta$  generate a path of quasi-continuously configurations where both energy and magnetization are allowed to relax self-consistently without any fixed constraint on the direction. The resulting curve in energy includes contributions from bilinear (BL) exchanges up to higher-order terms, e.g. BQ exchange interactions. We used different supercells that resulted in no variations of the results. We quantify the contribution of each kind of interactions using the

72 following non-Heisenberg spin Hamiltonian:

$$\mathcal{H} = - \sum_{ij} J_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j) - \sum_{ij} \lambda_{ij} S_i^z S_j^z - \sum_i D_i (\mathbf{S}_i \cdot \mathbf{e}_i)^2 - \sum_{ij} K_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j)^2 \quad (1)$$

73 where  $J_{ij}$  and  $\lambda_{ij}$  are the isotropic and anisotropic BL exchanges between spins  $\mathbf{S}_i$  and  $\mathbf{S}_j$  on  
 74 atomic sites  $i$  and  $j$ ;  $D_i$  is the on-site anisotropy with easy axis  $\mathbf{e}_i$ ; and  $K_{ij}$  is the BQ exchange  
 75 interactions which is due to electron hopping between two adjacent sites<sup>15</sup>. We restrict the discus-  
 76 sions to first nearest-neighbor BQ interactions, that is,  $K_{ij} = K_{bq}$ , and  $K_{ij} = 0$  otherwise. This  
 77 assumption has been shown to be sufficient to study a variety of magnetic systems with higher-  
 78 order exchanges<sup>5,6,8,9</sup>. We can write Eq.1 in a similar form separating the terms with angular and  
 79 non-angular dependence as  $E_{bq}^{tot}(\theta) = A_0^{bq} + A_1^{bq} \cdot S^2 \cos(\theta) + A_2^{bq} \cdot S^4 \cos^2(\theta)$ , where  $S$  is the  
 80 spin moment. The different coefficients can be interpreted as the corresponding amount of BL  
 81 ( $A_1^{bq}$ ) and BQ ( $A_2^{bq}$ ) exchanges, and the on-site energy as the spins are perpendicular to each other  
 82 ( $A_0^{bq}$ ). Supplementary Section 4 gives a thorough discussion on these coefficients and how to ex-  
 83 tract analytical equations for their interpretation using Eq.1. We extract  $A_0^{bq}$ ,  $A_1^{bq}$  and  $A_2^{bq}$  from  
 84 first-principles simulations for the variation of the total energy versus  $\theta$  (Supplementary Section  
 85 5).

86 We apply this procedure for a total of 50 compounds including the most common 2D mag-  
 87 nets studied up to date including several families of trihalides ( $\text{MX}_3$ ,  $\text{M}=\text{Ti, V, Cr, Mn, Fe, Ni,}$   
 88  $\text{Cu}$ ;  $\text{X}=\text{F, Cl, Br, I}$ ), metal tribromides ( $\text{MBr}_3$ ,  $\text{M}=\text{Mn, Cu, Fe, V}$ ), chromium based ternary tel-  
 89 lurides ( $\text{Cr}_2\text{X}_2\text{Te}_6$ ,  $\text{X}=\text{Ge, P, Si}$ ), metal based ternary chalcogenides ( $\text{M}_2\text{P}_2\text{X}_6$ ,  $\text{M}=\text{V, Cr, Mn,}$

90 Fe, Co, Ni; X=S, Se, Te), and transition metal dichalcogenides ( $\text{MX}_2$ , M=Co, Fe, V; X=S, Se,  
 91 Te) of different phases ( $2H$ ,  $1T$ ). Surprisingly, as the spins are spatially rotated away a sizable  
 92 deviation from a  $\cos \theta$ -like behavior characteristic of BL exchange interactions (shaded area) is  
 93 observed (Fig. **1b-e**). The overall trend seems independent of the stoichiometric formula or the  
 94 atomic elements composing the structure. The universal character of the higher-order exchange  
 95 process in layered materials can be appreciated clearer in Fig. **1f** where data-analytics using re-  
 96 gression algorithms (linear, quadratic, cubic) was evaluated over the computed data. The best  
 97 match between regression and DFT energies is for regressions beyond linear. This suggested that  
 98 even more complex magnetic interactions may take place in 2D magnetic materials such as 3-,  
 99 4-spin interactions<sup>16,17</sup>, and chiral biquadratic<sup>18,19</sup> which are not studied here. Materials with alike  
 100 chemical environment (e.g. bond lengths, electron affinity, binding energy) such as  $\text{CrI}_3$ ,  $\text{CrBr}_3$   
 101 and  $\text{CrCl}_3$  present close variation of the energy and consequently similar magnitudes of the BQ  
 102 exchange (Table 1). Other compounds tend to gain energy with the spin rotation and stabilize in a  
 103 different magnetic coupling, for instance,  $\text{CrF}_3$  (Fig. **1b**) becomes AFM ordered. This is also the  
 104 case of Mn-based compounds,  $2H\text{-MnS}_2$ ,  $2H\text{-MnSe}_2$ ,  $\text{MnPS}_3$ ,  $\text{MnPSe}_3$  (Fig. **1d-e**), which agreed  
 105 with magnetometry measurements<sup>20-22</sup>. It is noteworthy that  $\text{CuBr}_3$  and  $2H\text{-FeS}_2$  have substan-  
 106 tially larger magnitudes of BQ exchange (Table 1) comparable to more complex materials, i.e.  
 107 ferropnictides, where spin and electronic correlations are known to play a key role in the deter-  
 108 mination of their superconducting and strongly-correlated properties<sup>23</sup>. Both  $\text{CuBr}_3$  and  $2H\text{-FeS}_2$   
 109 have relatively small BL exchange in the range of 5.87 – 6.88 meV with  $S = 1$ . For materials with  
 110 small BL exchange higher-order exchange tends to be sizeable<sup>10</sup>. This result calls for further the-

oretical and experimental work on these two compounds whether unusual electronic interactions can be found. Furthermore, we noticed that several other compounds could not show a clear trend with  $\theta$  apart from those where a specific magnetic ordering is stabilized, e.g.  $\theta = 0, 180^\circ$  (Supplementary Section 6). Materials that are unable to stabilize different spin orientations are either due to strong magnetic anisotropy where a preferential spin orientation is too strong to be tilted (e.g. Ising magnets) or different spin solutions are not energetically stable ending up in non-magnetic phases<sup>24</sup>.

We have also checked whether other models can give a sound description of the magnetic properties of the quadratic dependence of the energy as a function of  $\theta$ . In particular, we considered two models: a Kitaev model<sup>25,26</sup>, and a Heisenberg model including biquadratic on-site magnetic anisotropy. For the latter, the magnitudes of the biquadratic on-site anisotropies are several orders of magnitude smaller than BQ exchange within the range  $3.87 - 14.32 \mu\text{eV}$  (see details in Supplementary Section 7). For the former, there is no quadratic dependence on  $\theta$  for the Kitaev model. We can expand the Kitaev Hamiltonian<sup>25</sup> assuming a rotation by angle  $\theta$  between the spins to show that a fitting equation of the form of  $E_{\text{Kitaev}}^{\text{tot}}(\theta) = B_0 + B_1 \sin(2\theta)$  can be extracted (see details in Supplementary Section 8). These results suggest that BL models are insufficient to describe the magnetic features of 2D vdW magnets.

**A Hubbard-based microscopic model** To understand the microscopic mechanism of the BQ exchange in 2D materials, we will use the following 2D half-filled Hubbard Hamiltonian applied



130 to the honeycomb lattice (Fig. 2a-b):

$$H = -t_{eff} \sum_{\langle ij \rangle, \sigma} c_{i,\sigma}^\dagger c_{j,\sigma} + U \sum_i n_{i\uparrow} n_{i\downarrow} + \sum_{i,\sigma} \mu_{i,\sigma} n_{i,\sigma}, \quad (2)$$

131 where indices  $i$  and  $j$  denote the lattice sites, the  $d$ -spin states on the metal atoms ( $M_{A,B}$ ) are  
 132 labeled as  $\sigma = \uparrow, \downarrow$ , the sum  $\langle ij \rangle$  is over the nearest neighbors and  $t_{eff}$  is the effective nearest  
 133 neighbor hopping between  $M_{A,B}$  ions.  $t_{eff}$  is due to the hybridization between  $3d^n$  and  $np$  orbitals  
 134 ( $n = 2, 3, 4, 5$  depending on the atomic element involved) at  $M_{A,B}$  and X atoms, respectively  
 135 (Fig. 2b). The direct hopping between  $M_{A,B}$  scales with  $t_{dd} \sim r^{-5}$  and therefore for relatively big  
 136 distances can be neglected<sup>15</sup>.  $U > 0$  is the non-negative on-site Coulomb repulsion,  $c_{i,\sigma}^\dagger (c_{i,\sigma})$  is  
 137 the creation (annihilation) operator for a fermion with spin  $\sigma$  at site  $i$ ,  $n = c_{i,\sigma}^\dagger c_{i,\sigma}$  is the density  
 138 operator and  $\mu_{i,\sigma}$  is the chemical potential which controls the filling of the bands. Second-order  
 139 perturbation theory in Eq. 2, assuming  $U \gg t_{eff}$ , gives the energy contributions of the Heisenberg  
 140 exchanges<sup>27,28</sup>:

$$\begin{aligned} J_{FM}^{(2)} &= t_{eff}^2 / (U - U_{ex}) \\ J_{AFM}^{(2)} &= t_{eff}^2 / (U + U_{ex}) \\ J_{bl} &= t_{eff}^2 \frac{2U_{ex}}{U^2 - U_{ex}^2} \end{aligned} \quad (3)$$

141 where  $J_{FM}^{(2)}$  and  $J_{AFM}^{(2)}$  are the exchange energies for FM and AFM coupling at second-order, and  
 142 the BL exchange is defined as  $J_{bl} = J_{FM}^{(2)} - J_{AFM}^{(2)}$ .  $U_{ex}$  is an energy correction for the internal spin  
 143 exchange whether a spin flip is required during the hopping between  $M_{A,B}$  sites (Fig. 2b)<sup>28</sup>. Such  
 144 term can be used to stabilize or destabilize spin transfer through the  $M_{A,B}$ —X covalent bonds as the  
 145 exchange occurs<sup>15,28</sup>. If the electron-hopping is to an occupied orbital of the neighboring site,  $U_{ex}$

will favor AFM alignment of the two spins via a superexchange interaction (see Supplementary Section 9 for details). However, if the electron-hopping is to an unoccupied or a virtual state, a FM alignment will be favored by  $U_{ex}$ <sup>29</sup>. The competition between the amount of energy  $U_{ex}$  to stabilize a specific coupling and the Coulomb repulsion  $U$  between the electrons at an energy state may compensate each other leading to a small value of  $J_{bl}$ . Indeed, several 2D magnets have shown low-temperature magnetism<sup>1,2,12</sup> which is directly related with the small magnitude of the exchange interactions. In this case, it is necessary to extend the perturbation in  $t_{eff}/U$  to fourth-order in Eq.2 involving at least one electron from both  $M_{A,B}$  sites which resulted in<sup>15</sup>:

$$\begin{aligned}
 J_{FM}^{(4)} &\propto t_{eff}^4 / (U - U_{ex})^3 \\
 J_{AFM}^{(4)} &\propto t_{eff}^4 / (U + U_{ex})^3 \\
 K_{bq} &= t_{eff}^4 \frac{2(3U^2U_{ex} + U_{ex}^3)}{(U^2 - U_{ex}^2)^3}
 \end{aligned} \tag{4}$$

with  $K_{bq} = J_{FM}^{(4)} - J_{AFM}^{(4)}$  being the BQ exchange energy. Both Eqs.3–4 show that a competition between FM and AFM couplings takes place once the electrons are hopping between different spin sites. The stabilization of one or another magnetic order is determined by several factors such as the ligand-field splitting  $\Delta_0$  between  $t_{2g}$  and  $e_g$  states in the metal atom in the honeycomb lattice. As the filling of both type of states determines the magnitude of the  $3d - sp$  hybridization between metals and ligands, we can approach  $\Delta_0 \approx U - U_{ex}$  being proportional to the bandgap of the material<sup>10</sup>. This condition is valid as long as the magnitudes of  $U$  and  $U_{ex}$  do not compete to each other. Since  $U_{ex}$  is an energy correction of spin stabilization, it should comply with Hund's rule where unpaired spins occupy other states of the  $3d$  shell (Fig. 2b). It has been shown that the role of high-order exchange interactions increases on reduction of the bandgap mediated by the

164 non-magnetic atoms which is related to the ratio of BQ and BL exchanges<sup>27,30</sup>. If we divide Eq.4  
 165 and Eq.3 and use the definition of  $\Delta_0$ , we can write a direct relationship between the exchange  
 166 interactions and the bandgap for 2D magnets as:

$$K_{\text{bq}}/J_{\text{bl}} = t_{\text{eff}} \frac{4U^2 + \Delta_0^2 - 2U\Delta_0}{\Delta_0^2(2U - \Delta_0)^2} \quad (5)$$

167 This equation can be understood as a direct interplay between the Coulomb repulsion and the  
 168 hopping of electrons between different sites subjected to the crystal field or bandgap of the material.  
 169 We can consider two situations in Eq.5:  $\Delta_0 \rightarrow 0$  and  $\Delta_0 \rightarrow 2U$  which correspond to small and  
 170 large bandgap materials, respectively. This resulted in:

$$K_{\text{bq}}/J_{\text{bl}} \propto t_{\text{eff}} \frac{1}{(\Delta_0)^2} \Big|_{\Delta_0 \rightarrow 0} \quad (6)$$

$$K_{\text{bq}}/J_{\text{bl}} \propto t_{\text{eff}} \frac{1}{(2U - \Delta_0)^2} \Big|_{\Delta_0 \rightarrow 2U} \quad (7)$$

171 Figure 2c shows the variation of  $K_{\text{bq}}/J_{\text{bl}}$  as a function of  $\Delta_0$  for the core of materials display-  
 172 ing BQ exchange interactions. Strikingly, both Eqs.6–7 correctly describes the overall behavior  
 173 observed in our simulations. Materials with similar bonding environment, for instance, either in  
 174 terms of Cr (Mn) atoms follow an increase (decrease) of  $K_{\text{bq}}/J_{\text{bl}}$  with the bandgap, respectively.  
 175 It is worth mentioning that as the compounds tend to a AFM spin alignment<sup>10,29</sup>, i.e.  $\text{CrF}_3$ , they  
 176 increase the value of  $K_{\text{bq}}/J_{\text{bl}}$  being the case within the Cr-based trihalide family ( $\text{CrX}_3$ , X=F, Cl,  
 177 Br, I). There is also an abrupt change in behavior for narrow bandgap materials and metals with no  
 178 dependence on  $\Delta_0$  (inset in Fig. 2c). These results indicate that one can design the amount of BQ  
 179 exchange in a 2D magnet tuning its bandgap, for instance using an electric bias as recently used in  
 180  $\text{CrI}_3$ <sup>31</sup>.

**Thermal effects in 2D magnets** To verify whether BQ exchange interactions will have any effect on the thermal properties of 2D vdW magnets, we have implemented Eq.1 within the Monte Carlo Metropolis algorithm with an adaptive move<sup>32</sup>. In the spin model we assume a classical spin vector  $\mathbf{S}_i$  on each atomic site  $i$ . The quantization vector for the spin is a local quantity which intrinsically includes the effects of local thermal spin fluctuations, magnon processes and spin excitations. In our implementation the BQ exchange is quite general and can be applied to any pair-wise exchange interaction of arbitrary range. We also consider an additional term in Eq.1 including the local Zeeman field  $\mathbf{B}$  on the magnetic ions with a length of the local atomic moment  $\mu_i$  arising from the BQ exchange interactions as:

$$\mathcal{H} = - \sum_{ij} J_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j) - \sum_{ij} \lambda_{ij} S_i^z S_j^z - \sum_i D_i (\mathbf{S}_i \cdot \mathbf{e}_i)^2 - \sum_{ij} K_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j)^2 - \sum_i \mu_i \mathbf{S}_i \cdot \mathbf{B}_i \quad (8)$$

For atomistic spin dynamics simulations, the effective field due to the biquadratic exchange are calculated via the first-derivative of Eq.8 on the different spin components as:

$$H_{bq,i}^l = - \frac{1}{\mu_i} \frac{\partial \mathcal{H}}{\partial S_i^l} = 2K_{bq} S_j^l (\mathbf{S}_i \cdot \mathbf{S}_j) \quad (9)$$

where  $l = x, y, z$  represents the geometrical coordinates at the atomic sites  $i(j)$ , and  $(\mathbf{S}_i \cdot \mathbf{S}_j) = S_i^x S_j^x + S_i^y S_j^y + S_i^z S_j^z$ . The effective field  $H_{bq,i}^l$  therefore contributes to the total field describing the time evolution of each atomic spin using the stochastic Landau-Lifshitz-Gilbert equation<sup>33</sup>. We calculate up to third nearest-neighbors  $\lambda_{ij}$  and  $J_{ij}$  in Eq.1 on a representative set of 2D magnets, e.g. Cr-based trihalide family (Table 2). Supplementary Section 10 gives a thorough discussion on the calculation of the exchange parameters. Figure 3 shows the behavior of the magnetization ( $M/M_0$ , where  $M_0$  is the saturation magnetization at 0 K) and the logarithm of the magnetic susceptibility ( $\ln \chi$ ) as a function of temperature T(K) for CrI<sub>3</sub>, CrBr<sub>3</sub> and CrCl<sub>3</sub>. Intriguingly, the inclusion

of BQ exchange interactions give sizable thermal effects on both  $M/M_0$  and  $\ln \chi$  for all materials (Supplementary Section 11). By fitting the Monte Carlo simulations with  $M(T) = M_0 \left(1 - \frac{T}{T_c}\right)^\beta$  (where  $\beta$  is the critical exponent) we can notice that the Curie temperatures  $T_c$  changes by several Kelvins with the inclusion of BQ exchange interactions. The calculated magnitudes of  $T_c$  for  $\text{CrI}_3$  and  $\text{CrBr}_3$  approach closely those measured for both compounds with almost no difference (Fig. 3a-d). The lack of experimentally measured  $T_c$  for monolayer  $\text{CrCl}_3$  unable us to make a clear comparison with our simulations. The different amount of nearest-neighbors at BL exchanges (from 1st to 3rd) also produces substantial effects even though not enough to reproduce the experimental values of  $T_c$  for  $\text{CrI}_3$  and  $\text{CrBr}_3$ . It is worth mentioning that different groups have reported distinct magnitudes of  $T_c$  for  $\text{CrBr}_3$ <sup>34–36</sup>, which may be due to different factors such as sample quality, defects, and doping levels. We believe that our simulations still provide an accurate picture showing the effects of the underlying exchange interactions for these low-dimensional magnets at the limit of an ideal, pristine crystal (see Supplementary Section 12). Moreover, several other materials display larger values of BQ exchange interactions (Table 1) indicating that higher-order exchange interactions should be taken into account on the description of their magnetic properties.

**Enhancement of magnetic stability** An outstanding remark on the existence of BQ interactions in 2D magnets is on the implications on their magnetic features. It is well known that several materials developed macroscopic properties due to this higher-order exchange interactions. From paramagnetic measurements of  $\text{Mn}^{+2}$  ions in  $\text{MgO}$ <sup>9</sup>, up to different magnetic phases in oxides<sup>5,13,37</sup>, it is not clear whether BQ exchange induces any significant role effect on basic properties, such as critical temperatures or stability. To understand the intrinsic effect of higher-order exchange

interactions in the thermal features of 2D magnetic materials and provide a consistent description of the underlying spin interactions, we have developed an analytical model based on spin-wave theory<sup>38,39</sup>. We generalized Eq.1 to second order contributions on the magnetic anisotropies which resulted in:

$$\begin{aligned} \mathcal{H} = & - \sum_{ij} J_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j) - \sum_{ij} \lambda_{ij} S_i^z S_j^z - \sum_i D_i (\mathbf{S}_i \cdot \mathbf{e}_i)^2 \\ & - \sum_{ij} K_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j)^2 - \sum_i D_i^{bq} (\mathbf{S}_i \cdot \mathbf{e}_i)^4 - \sum_{ij} \lambda_{ij}^{bq} (S_i^z S_j^z)^2 \end{aligned} \quad (10)$$

where  $D_i^{bq}$  and  $\lambda_{ij}^{bq}$  are the BQ on-site anisotropy and BQ anisotropic exchange, respectively. We replace the spin operators  $\mathbf{S}_{i,j}$  in Eq.10 by bosonic creation ( $a_i^\dagger, b_i^\dagger$ ) and annihilation ( $a_i, b_i$ ) operators over the honeycomb sub-lattices  $\mathcal{A}$  and  $\mathcal{B}$  using Holstein-Primakoff transformations<sup>39</sup>:

**For  $i \in \mathcal{A}$  sublattice:**

**For  $i \in \mathcal{B}$  sublattice:**

$$S_i^z = (S - a_i^\dagger a_i)$$

$$S_i^z = (S - b_i^\dagger b_i)$$

$$S_i^+ \approx \sqrt{2S} a_i$$

$$S_i^+ \approx \sqrt{2S} b_i$$

$$S_i^- \approx a_i^\dagger \sqrt{2S}$$

$$S_i^- \approx b_i^\dagger \sqrt{2S}$$

where we assume that  $a_i^\dagger a_i \ll S$  and  $b_i^\dagger b_i \ll S$  for small deviations of the spins from their ground state orientations. This gives (see Supplementary Section 13 for details):

$$\tilde{\mathcal{H}} = \sum_i \left( 2\tilde{D}S + Z \cdot S(\tilde{J} + \tilde{\lambda}) \right) (b_i^\dagger b_i + a_i^\dagger a_i) - \tilde{J}S \sum_{\langle ij \rangle} \left( a_i^\dagger b_j + b_j^\dagger a_i \right) \quad (11)$$

where the sum over  $i$  and  $j$  runs over the sub-lattices and first nearest neighbors, respectively, and  $Z$  is the number of first nearest-neighbors. This procedure outlines a strong implication of the

inclusion of higher-order exchange interactions in the description of the magnetic properties of 2D magnets. That is, the enhancement of several magnetic quantities:

$$\tilde{J} \approx J + 2S^2 \cdot K_{\text{bq}} \quad (12)$$

$$\tilde{\lambda} \approx \lambda + 2S^2 \cdot \lambda^{\text{bq}} \quad (13)$$

$$\tilde{D} \approx D + 2S^2 \cdot D^{\text{bq}} \quad (14)$$

where  $\lambda^{\text{bq}}$  and  $D^{\text{bq}}$  are the BQ anisotropic exchanges, and the BQ on-site magnetic anisotropy, respectively, for first nearest neighbors. Incidentally Eqs.12–14 yield several implications on the magnetic properties of the sheets, in particular, on the stabilization of magnetism in truly 2D. It is well known that in order to overcome thermal fluctuations that could destroy any magnetic order<sup>40</sup>, sizable magnetic anisotropies need to be developed to gap the low-energy modes in the magnon spectra. That is, a spin wave gap needs to appear at the energy dispersion to act as a barrier to excitations of long-wavelength spin waves. We can show that the relation between the spin wave gap taken into account BQ exchange interactions ( $\Delta_{\text{bq}}$ ) and that at the level BL exchange ( $\Delta_{\text{bl}}$ ) for first-nearest neighbors is given by (see Supplementary Section 13):

$$\Delta_{\text{bq}} = \Delta_{\text{bl}} + 4S^3(D^{\text{bq}} + \frac{3}{2}\lambda^{\text{bq}}) \quad (15)$$

where  $\Delta_{\text{bl}} = 2S[D + \frac{Z\lambda}{2}]$ . By using some parameters for monolayer  $\text{CrI}_3$  from Table 2, and approaching the second term in Eq.15 as  $D^{\text{bq}} + 3\lambda^{\text{bq}} \approx 10.72 \mu\text{eV}$  (see Supplementary Section 7) we can estimate  $\Delta_{\text{bl}} = 0.81 \text{ meV}$  and  $\Delta_{\text{bq}} = 1.0 \text{ meV}$ . The magnitude of  $\Delta_{\text{bq}}$  is consistent with recent measurements of the magnon dispersion for bulk  $\text{CrI}_3$ , which a spin wave gap of approximately 1.3 meV was measured<sup>41</sup>. Furthermore, the increment of the on-site and anisotropic magnetic

anisotropies (Eqs.13–14) indicates that not only spin-orbit mechanisms are behind the substantial anisotropy in CrI<sub>3</sub> but rather higher-order exchange processes. Such BQ exchange-driven large magnetic anisotropy mechanism has been proposed for iron-based superconductors<sup>7,23,42</sup> which successfully described their magnetic properties. A direct consequence Eqs.12–14 is the increment of Curie temperatures by factor  $r$  given by (see Supplementary Section 13):

$$r = \frac{\tilde{T}_C}{T_C} \approx \frac{\tilde{J} \ln(1 + 2\pi JS/\Delta_{bl})}{J \ln(1 + 2\pi \tilde{J} S/\Delta_{bq})}. \quad (16)$$

where  $\tilde{T}_C$  and  $T_C$  are the Curie temperatures with and without BQ interactions, respectively. Including few values in Eq.16, we can roughly estimate an enhancement of  $r \approx 39\%$  for monolayer CrI<sub>3</sub> which follows the Monte Carlo calculations (Fig. 3a-b). It is worth noticing that the model in Eq. 11, *i*) takes into account only first-nearest neighbors in the exchange interactions, and *ii*) we assume a mean-field approach in the solution of the non-linear Holstein-Primakoff transformation (e.g. magnon-magnon interactions) to simplify the complex mathematical terms, i.e. four-operator product. Supplementary Section 14 provides a full discussion on the details involved.

**Describing topological spin excitations through BQ and DMI** An intriguing question that raised by the presence of BQ exchange interactions is whether they play an important role in the description of magnetic quasiparticles such as magnons and non-trivial spin textures in 2D vdw magnets. It has recently been shown using neutron scattering<sup>41</sup> that CrI<sub>3</sub> magnet shows topological spin-excitations with two distinctive magnon bands separated by a bandgap of 4 meV at the Dirac **K**-point. In spite of the clear demonstration that CrI<sub>3</sub> can not follow an Ising model as initially pointed out<sup>1</sup>, these results indicate that non-Heisenberg interactions play an important role in the creation of spin-excitations in 2D magnetic materials. Since the gap opening at **K** is related with



the inversion symmetry breaking and appearance of DMI, chirality becomes crucial in the discrimination of the magnon bound states. Moreover, it has become well established<sup>23,43–45</sup> that isotropic spin interactions at the level of the BL Heisenberg models do not capture all features in the energy dispersion of spin-excitations in magnetic materials. There are additional contributions through uniaxial anisotropies, next-nearest neighbor interactions and the delicate balance between them, that need to be considered. In order to account for all these quantities, we extended the model in Eq.1 with the addition of DMI:

$$\mathcal{H}_{\text{latt}} = \mathcal{H} + \sum_{\langle\langle ij \rangle\rangle} \mathbf{A}_{ij} \cdot (\mathbf{S}_i \times \mathbf{S}_j) \quad (17)$$

where  $\mathbf{A}_{ij}$  is the DMI between spins  $\mathbf{S}_i$  and  $\mathbf{S}_j$ . For a honeycomb ferromagnetic layer, with an easy axis perpendicular to the surface ( $\mathbf{z}$ -direction), there is no breaking of the inversion symmetry of the lattice at first nearest-neighbors, e.g.  $\mathbf{A}_{ij}^{1st} = 0$ . However, contributions from the second nearest-neighbors become non-negligible as space inversion is not present. Therefore, we consider the DMI vector as  $\mathbf{A} = \nu_{ij} A_z \mathbf{z}$ , where  $A_z$  is the magnitude of the DMI along of the easy-axis, and  $\nu_{ij} = \pm 1$  represents the hopping of spins at second nearest-neighbors from sites  $i$  to  $j$  and vice-versa, respectively (Fig. 2a). Similarly as shown above, we can use Holstein-Primakoff transformations for  $J_i > 0$  to write Eq.17 in terms of bosonic creation and annihilation operators (see details in Supplementary Section 15):

$$\mathcal{H}_{\text{latt}} = \mathcal{H}_{BL} + \mathcal{H}_{BQ} + \mathcal{H}_{DMI} \quad (18)$$

where we separate the terms due to BL exchange ( $\mathcal{H}_{BL}$ ), from those due to BQ ( $\mathcal{H}_{BQ}$ ) and DMI ( $\mathcal{H}_{DMI}$ ) which can be written as:

$$\mathcal{H}_{BL} = H_D + \sum_{i=1}^3 H_i^{Isotropic} + \sum_{i=1}^3 H_i^{Anisotropic} \quad (19)$$

$$H_{BQ} = -12K_{bq}S^4 - 2K_{bq}S^3 \left( \sum_{\langle ij \rangle} (b_j^\dagger a_i + a_i^\dagger b_j) - Z_1 \sum_{i \in \mathcal{A}} a_i^\dagger a_i - Z_1 \sum_{i \in \mathcal{B}} b_i^\dagger b_i \right) \quad (20)$$

$$\mathcal{H}_{DMI} = iA_z S \left( \sum_{\langle\langle ij \rangle\rangle \in \mathcal{A}} (a_i^\dagger a_j - a_j^\dagger a_i) + \sum_{\langle\langle ij \rangle\rangle \in \mathcal{B}} (b_i^\dagger b_j - b_j^\dagger b_i) \right) \quad (21)$$

where  $H_D$  is the on-site anisotropy term, and  $H_i^{Isotropic}$  and  $H_i^{Anisotropic}$  are respectively the isotropic and anisotropic parts of the BL exchange Hamiltonian taken into account up to third nearest-neighbors ( $i = 1, 2, 3$ ). The sum in  $\langle ij \rangle$  runs over the first nearest-neighbors at both sublattices  $\mathcal{A}$  and  $\mathcal{B}$  while that on  $\langle\langle ij \rangle\rangle$  runs over the second nearest-neighbors specifically on either  $\mathcal{A}$  or  $\mathcal{B}$  lattice. We notice that the second nearest neighbors not only break the inversion symmetry of the honeycomb lattice but also generate a magnetic flux  $\phi$  involving  $A_z$  and  $J_2$  given by:

$$\phi = \tan^{-1}(A_z/J_2) \quad (22)$$

The magnetic flux (circular arrow) can be appreciated in Fig. 2a when the magnons (dashed lines) hop between the second nearest-neighbors. This process introduces a phase  $\phi_{ij} = \mu_{ij}\phi$  ( $\mu_{ij} = \pm 1$ ) in the magnons as they hop from a site  $i$  to  $j$ , and vice-versa. The different magnitudes of  $\mu_{ij}$  determine whether the hopping follows the flux and consequently induces nontrivial topological

properties (e.g. chirality) similarly as in the Haldane model<sup>46,47</sup> for fermions. The topological features of the magnon bands can be described in the  $\mathbf{k}$ -space by using the Fourier transform of the creation ( $a_{\mathbf{k}}^\dagger, b_{\mathbf{k}}^\dagger$ ) and annihilation ( $a_{\mathbf{k}}, b_{\mathbf{k}}$ ) operators in Eq.18 as:

$$\mathcal{H} = \mathcal{H}_0 + \sum_{\mathbf{k}} \begin{pmatrix} a_{\mathbf{k}}^\dagger & b_{\mathbf{k}}^\dagger \end{pmatrix} \begin{pmatrix} h_0(\mathbf{k}) + h_z(\mathbf{k}) & h_x(\mathbf{k}) - ih_y(\mathbf{k}) \\ h_x(\mathbf{k}) + ih_y(\mathbf{k}) & h_0(\mathbf{k}) - h_z(\mathbf{k}) \end{pmatrix} \begin{pmatrix} a_{\mathbf{k}} \\ b_{\mathbf{k}} \end{pmatrix} \quad (23)$$

where the different terms can be written as (see Supplementary Section 15 for details):

$$\begin{aligned} \mathcal{H}_0 &= -2DS - 3(J_1 + \lambda_1)S^2 - 6(J_2 + \lambda_2)S^2 - 12KS^4 \\ h_0(\mathbf{k}) &= \varepsilon_0 - 4\sqrt{(J_2S)^2 + (A_zS)^2}C(\mathbf{k}) \\ \varepsilon_0 &= 2DS + (J_1 + \lambda_1)Z_1S + 6KS^3 + 6(J_2 + \lambda_2)S + 3J_3S \\ h_x(\mathbf{k}) &= -(J_1 + 2KS^2)S \sum_{j=1}^3 \cos(\mathbf{k} \cdot \boldsymbol{\tau}_j) - J_3S \sum_{j=1}^3 \cos(\mathbf{k} \cdot (\mathbf{u}_j + \boldsymbol{\tau}_j)) \\ h_y(\mathbf{k}) &= -(J_1 + 2KS^2)S \sum_{j=1}^3 \sin(\mathbf{k} \cdot \boldsymbol{\tau}_j) - J_3S \sum_{j=1}^3 \sin(\mathbf{k} \cdot (\mathbf{u}_j + \boldsymbol{\tau}_j)) \\ h_z(\mathbf{k}) &= 4\sqrt{(J_2S)^2 + (A_zS)^2}S(\mathbf{k}) \end{aligned} \quad (24)$$

where  $C(\mathbf{k}) = \cos(\phi) \sum_{j=1}^3 \cos(\mathbf{k} \cdot \mathbf{u}_j)$  and  $S(\mathbf{k}) = \sin(\phi) \sum_{j=1}^3 \sin(\mathbf{k} \cdot \mathbf{u}_j)$ . The vectors  $\boldsymbol{\tau}_j$  and  $\mathbf{u}_j$  are respectively between 1<sup>st</sup> and 2<sup>nd</sup> nearest neighbors (Fig. 2a).

The eigenvalues of Eq.23 can be written in terms of the lower and upper energy bands as:

$$E^\pm = h_0(\mathbf{k}) \pm \sqrt{h_x(\mathbf{k})^2 + h_y(\mathbf{k})^2 + h_z(\mathbf{k})^2} \quad (25)$$

Note that Eqs.24 and Eq.25 are general for any honeycomb material with ferromagnetic order, easy-axis perpendicular to the surface and develop DMI and BQ exchange interactions. For instance, we can use them to predict the energy dispersion of the magnon bands over the first Brill-

311 lounin zone (BZ) of any 2D magnet, e.g.  $\text{CrI}_3$ . Figure 4a-e shows different levels of theory either  
 312 using a simple XXZ model or including more sophisticated terms through the BQ exchange, DMI  
 313 or simultaneously all of them. It is clear that XXZ models without any contribution from DMI  
 314 (Fig. 4a-c) does not describe the gap opening at the Dirac points due to the breaking of the in-  
 315 version symmetry. Moreover, a model at the level of XXZ+DMI as initially used to understand  
 316 the magnon dispersion of  $\text{CrI}_3$ <sup>41</sup> does not capture entirely the full profile of the bands (Fig. 4d).  
 317 The upper branch  $E^+$  becomes nearly flat with the increment of  $J_2$  at the path  $K - M - K$  while  
 318 the lower magnon branch  $E^-$  turns more curved. This picture modifies substantially when BQ  
 319 exchange interactions are included in the XXZ+BQ+DMI model (Fig. 4e) as the magnon bands  
 320 follow a similar curvature throughout the variation of  $J_2$ , although the upper branch at  $\Gamma$  increased  
 321 to  $E_{\Gamma}^+ = 27.8$  meV. A sound comparison between the XXZ+BQ+DMI model and the experimental  
 322 results for  $\text{CrI}_3$  is obtained (Fig. 4f) when  $J_1$  is varied similarly (Fig. 4a) indicating that the first  
 323 nearest-neighbors are important on the stabilization of  $E_{\Gamma}^+$ . It is worth mentioning that the value  
 324 of the exchange interactions taken into account in the fitting of the neutron scattering spectra<sup>41</sup>  
 325 do not separate BL contributions from BQ as shown in Eq.12-14. Hence, it is not known from  
 326 the fitting procedure<sup>41</sup> what is the contribution of  $K_{bq}$  to the magnon dispersion. However, such  
 327 separation can be clearly stated in our model as indicated in Fig. 4f. Furthermore, even though  
 328 DMI is important for the gap opening at the Dirac point, it does not contribute to the magnitudes of  
 329 the magnetization or critical temperatures for any 2D magnet with an out-of-plane easy-axis and  
 330 ferromagnetic aligned spins (see details in Supplementary Section 15).

## Discussion

In summary, we have shown the importance of biquadratic exchange interaction in the magnetic properties of 2D materials. We have described the phenomenology of such higher-order spin coupling, discussed its implications on several magnetic properties, and presented results at the level of non-collinear first-principles methods, Monte Carlo approximations and analytical models. The developed spin Hamiltonian including BQ exchange and DMI provided an accurate picture of topological spin-excitations on a generalized basis for any 2D magnet. Our results are particularly timely given the increasing interest in quantum materials, and we believe that our work will motivate the exploration of different exchange couplings and competition between critical phenomena<sup>48</sup>.

The effects of the BQ exchange interactions proposed here should manifest in experimentally accessible temperature range. One indication is already the accurate reproduction of experimental Curie temperatures<sup>1,35</sup> including higher-order exchange which could not be obtained at the level of Ising, Heisenberg or Kitaev models. The magnitudes of BQ exchange can be in principle extracted from accurate hysteresis loops using phenomenological models<sup>49,50</sup>. Importantly in such analysis are potential temperature variations of BL and BQ exchanges with layer thickness which may indicate tunable interlayer exchanges still to be explored in 2D magnets. Frustrated 2D Heisenberg models in the presence of BQ exchange interactions are also a non-trivial matter with a rich phase diagram involving incommensurate spin spirals, canted ferromagnetic states, quadrupolar phase or vertexes<sup>23,51-53</sup>. As our results indicate that BQ exchanges are important for 2D magnets, possible

ordered and disordered magnetic regimes may be stabilized in appreciable temperatures. Moreover, it is possible to enhance or suppress BQ interactions in Mott-Hubbard systems by applying external electric fields<sup>54</sup>. Indeed, the control of the magnetic properties of CrI<sub>3</sub> using electrical means has already been demonstrated<sup>31</sup>. Therefore, this opens the prospect of a coherent transfer between spin and charge degrees of freedom using short laser pulses in nanosheets.

**Methods** All methods can be found in Supplementary Materials.

**Data Availability** The data that support the findings of this study are available within the paper and its Supplementary Information.

**Acknowledgements** EJGS acknowledges computational resources through the UK Materials and Molecular Modelling Hub for access to THOMAS supercluster, which is partially funded by EPSRC (EP/P020194/1); CIRRUS Tier-2 HPC Service (ec131 Cirrus Project) at EPCC (<http://www.cirrus.ac.uk>) funded by the University of Edinburgh and EPSRC (EP/P020267/1); ARCHER UK National Supercomputing Service (<http://www.archer.ac.uk>) via Project d429. EJGS acknowledges the EPSRC Early Career Fellowship (EP/T021578/1) and the University of Edinburgh for funding support.

**Competing interests** The Authors declare no conflict of interests.

**Author Contributions** EJGS conceived the idea, supervised the project and undertook the analysis. AK performed the first-principles and Monte Carlo simulations under the supervision of EJGS. RFLE implemented the biquadratic exchange interactions in the Monte Carlo algorithm. MA, AK

369 and EJGS developed the analytical and numerical models used to describe the biquadratic ex-  
370 change and DMI. KSN contributed on the discussions and significance of the results. EJGS wrote  
371 the paper with inputs from all authors. All authors contributed to this work, read the manuscript,  
372 discussed the results, and agreed to the contents of the manuscript.

## References

1. Huang, B. *et al.* Layer-dependent ferromagnetism in a van der waals crystal down to the monolayer limit. *Nature* **546**, 270–274 (2017).
2. Gong, C. *et al.* Discovery of intrinsic ferromagnetism in two-dimensional van der waals crystals. *Nature* **546**, 265–269 (2017).
3. Guguchia, Z. *et al.* Magnetism in semiconducting molybdenum dichalcogenides. *Sci. Adv.* **4**, 1–8 (2018).
4. Slonczewski, J. C. Fluctuation mechanism for biquadratic exchange coupling in magnetic multilayers. *Phys. Rev. Lett.* **67**, 3172–3175 (1991).
5. Fedorova, N. S., Ederer, C., Spaldin, N. A. & Scaramucci, A. Biquadratic and ring exchange interactions in orthorhombic perovskite manganites. *Phys. Rev. B* **91**, 165122–165136 (2015).
6. Wysocki, A. L., Belashchenko, K. D. & Antropov, V. P. Consistent model of magnetism in ferropnictides. *Nat. Phys.* **7**, 485–489 (2011).
7. Zhu, H.-F. *et al.* Giant biquadratic interaction-induced magnetic anisotropy in the iron-based superconductor  $A_x\text{Fe}_{2-y}\text{Se}_2$ . *Phys. Rev. B* **93**, 024511–024517 (2016).
8. Turner, A. M., Wang, F. & Vishwanath, A. Kinetic magnetism and orbital order in iron telluride. *Phys. Rev. B* **80**, 224504–224513 (2009).
9. Harris, E. A. & Owen, J. Biquadratic exchange between  $\text{Mn}^{2+}$  ions in  $\text{MgO}$ . *Phys. Rev. Lett.* **11**, 9–10 (1963).



- 392 10. Nagaev, É. L. Anomalous magnetic structures and phase transitions in non-heisenberg mag-  
393 netic materials. *Soviet Physics Uspekhi* **25**, 31–57 (1982).
- 394 11. Gong, C. & Zhang, X. Two-dimensional magnetic crystals and emergent heterostructure de-  
395 vices. *Science* **363**, 1–11 (2019).
- 396 12. Gibertini, M., Koperski, M., Morpurgo, A. F. & Novoselov, K. S. Magnetic 2d materials and  
397 heterostructures. *Nat. Nanotechnol.* **14**, 408–419 (2019).
- 398 13. Hellsvik, J. *et al.* Tuning order-by-disorder multiferroicity in cuo by doping. *Phys. Rev. B* **90**,  
399 014437–014446 (2014).
- 400 14. Novák, P., Chaplygin, I., Seifert, G., Gemming, S. & Laskowski, R. Ab-initio calculation of  
401 exchange interactions in ymno3. *Comp. Mat. Sci.* **44**, 79 – 81 (2008).
- 402 15. Takahashi, M. Half-filled hubbard model at low temperature. *J. Phys. C: Sol. St. Phys.* **10**,  
403 1289–7301 (1977).
- 404 16. Krönlein, A. *et al.* Magnetic ground state stabilized by three-site interactions: Fe/Rh(111).  
405 *Phys. Rev. Lett.* **120**, 207202–207206 (2018).
- 406 17. Kurz, P., Bihlmayer, G., Hirai, K. & Blügel, S. Three-dimensional spin structure on a two-  
407 dimensional lattice: Mn /cu(111). *Phys. Rev. Lett.* **86**, 1106–1109 (2001).
- 408 18. Brinker, S., dos Santos Dias, M. & Lounis, S. The chiral biquadratic pair interaction. *New J.*  
409 *Phys.* **21**, 083015–083037 (2019).

- 410 19. Grytsiuk, S. *et al.* Topological–chiral magnetic interactions driven by emergent orbital mag-  
411 netism. *Nat. Commun.* **11**, 511–518 (2020).
- 412 20. Kim, K. *et al.* Antiferromagnetic ordering in van der waals 2d magnetic material MnPS3  
413 probed by raman spectroscopy. *2D Mater.* **6**, 041001–041009 (2019).
- 414 21. Makimura, C., Sekine, T., Tanokura, Y. & Kurosawa, K. Raman scattering in the two-  
415 dimensional antiferromagnet MnPSe3. *J. Phys.: Cond. Matt.* **5**, 623–632 (1993).
- 416 22. Hastings, J. M., Elliott, N. & Corliss, L. M. Antiferromagnetic structures of  $\text{MnS}_2$ ,  $\text{MnSe}_2$ , and  
417  $\text{MnTe}_2$ . *Phys. Rev.* **115**, 13–17 (1959).
- 418 23. Wysocki, A. L., Belashchenko, K. D. & Antropov, V. P. Consistent model of magnetism in  
419 ferropnictides. *Nat. Phys.* **7**, 485–489 (2011).
- 420 24. Kurz, P., Bihlmayer, G., Hirai, K. & Blügel, S. Three-dimensional spin structure on a two-  
421 dimensional lattice:  $\text{Mn}/\text{Cu}(111)$ . *Phys. Rev. Lett.* **86**, 1106–1109 (2001).
- 422 25. Kitaev, A. Anyons in an exactly solved model and beyond. *Ann. Phys.* **321**, 2 – 111 (2006).
- 423 26. Xu, C., Feng, J., Xiang, H. & Bellaiche, L. Interplay between kitaev interaction and single  
424 ion anisotropy in ferromagnetic  $\text{CrI}_3$  and  $\text{CrGeTe}_3$  monolayers. *npj Comput. Mater.* **4**, 57–63  
425 (2018).
- 426 27. Anderson, P. W. New approach to the theory of superexchange interactions. *Phys. Rev.* **115**,  
427 2–13 (1959).
- 428 28. Dionne, G. F. *Magnetic Oxides* (Springer, Boston, MA, 2009).

- 429 29. Mila, F. & Zhang, F.-C. On the origin of biquadratic exchange in spin 1 chains. *Eur. Phys. J.*  
430 *B* **16**, 7–10 (2000).
- 431 30. Anderson, P. W. Theory of magnetic exchange interactions: exchange in insulators and semi-  
432 conductors. In Seitz, F. & Turnbull, D. (eds.) *Sol. St. Phys.*, vol. 14 of *Solid State Physics*, 99  
433 – 214 (Academic Press, 1963).
- 434 31. Jiang, S., Shan, J. & Mak, K. F. Electric-field switching of two-dimensional van der waals  
435 magnets. *Nat. Mater.* **17**, 406–410 (2018).
- 436 32. Evans, R. F. *et al.* Atomistic spin model simulations of magnetic nanomaterials. *J. Phys.:*  
437 *Cond. Matt.* **26**, 103202–103225 (2014).
- 438 33. Ellis, M. O. A. *et al.* The landau–lifshitz equation in atomistic models. *Low Temp. Phys.* **41**,  
439 705–712 (2015).
- 440 34. Kim, H. H. *et al.* Evolution of interlayer and intralayer magnetism in three atomically thin  
441 chromium trihalides. *PNAS* **116**, 11131–11136 (2019).
- 442 35. Kim, M. *et al.* Micromagnetometry of two-dimensional ferromagnets. *Nat. Electron.* **2**, 457–  
443 463 (2019).
- 444 36. Zhang, Z. *et al.* Direct photoluminescence probing of ferromagnetism in monolayer two-  
445 dimensional crbr<sub>3</sub>. *Nano Lett.* **19**, 3138–3142 (2019).

- 446 37. Mochizuki, M., Furukawa, N. & Nagaosa, N. Theory of electromagnons in the multiferroic  
447 mn perovskites: The vital role of higher harmonic components of the spiral spin order. *Phys.*  
448 *Rev. Lett.* **104**, 177206–177210 (2010).
- 449 38. Dyson, F. J. General theory of spin-wave interactions. *Phys. Rev.* **102**, 1217–1230 (1956).
- 450 39. Holstein, T. & Primakoff, H. Field dependence of the intrinsic domain magnetization of a  
451 ferromagnet. *Phys. Rev.* **58**, 1098–1113 (1940).
- 452 40. Mermin, N. D. & Wagner, H. Absence of ferromagnetism or antiferromagnetism in one- or  
453 two-dimensional isotropic heisenberg models. *Phys. Rev. Lett.* **17**, 1133–1136 (1966).
- 454 41. Chen, L. *et al.* Topological spin excitations in honeycomb ferromagnet  $\text{CrI}_3$ . *Phys. Rev. X* **8**,  
455 041028–041035 (2018).
- 456 42. Hu, J., Xu, B., Liu, W., Hao, N.-N. & Wang, Y. Unified minimum effective model of magnetic  
457 properties of iron-based superconductors. *Phys. Rev. B* **85**, 144403–144415 (2012).
- 458 43. Elliott, R. J. & Thorpe, M. F. The effects of magnon-magnon interaction on the two-magnon  
459 spectra of antiferromagnets. *J. Phys. C: Sol. St. Phys.* **2**, 1630–1643 (1969).
- 460 44. Nauciel-Bloch, M., Sarma, G. & Castets, A. Spin-one heisenberg ferromagnet in the presence  
461 of biquadratic exchange. *Phys. Rev. B* **5**, 4603–4609 (1972).
- 462 45. Coldea, R. *et al.* Spin waves and electronic interactions in  $\text{La}_2\text{CuO}_4$ . *Phys. Rev. Lett.* **86**, 5377–  
463 5380 (2001).

- 464 46. Haldane, F. D. M. Model for a quantum hall effect without landau levels: Condensed-matter  
465 realization of the "parity anomaly". *Phys. Rev. Lett.* **61**, 2015–2018 (1988).
- 466 47. Owerre, S. A. Topological honeycomb magnon hall effect: A calculation of thermal hall  
467 conductivity of magnetic spin excitations. *J. Appl. Phys.* **120**, 043903–043908 (2016).
- 468 48. Basov, D. N., Averitt, R. D. & Hsieh, D. Towards properties on demand in quantum materials.  
469 *Nat. Mater.* **16**, 1077–1088 (2017).
- 470 49. Strijkers, G. J., Kohlhepp, J. T., Swagten, H. J. M. & de Jonge, W. J. M. Origin of biquadratic  
471 exchange in Fe/Si/Fe. *Phys. Rev. Lett.* **84**, 1812–1815 (2000).
- 472 50. Fullerton, E. E. & Bader, S. D. Temperature-dependent biquadratic coupling in antiferromag-  
473 netically coupled fe/fesi multilayers. *Phys. Rev. B* **53**, 5112–5115 (1996).
- 474 51. Hayden, L. X., Kaplan, T. A. & Mahanti, S. D. Frustrated classical heisenberg and  $xy$  models  
475 in two dimensions with nearest-neighbor biquadratic exchange: Exact solution for the ground-  
476 state phase diagram. *Phys. Rev. Lett.* **105**, 047203–047207 (2010).
- 477 52. Kaplan, T. Frustrated classical heisenberg model in one dimension with nearest-neighbor  
478 biquadratic exchange: Exact solution for the ground-state phase diagram. *Phys. Rev. B* **80**,  
479 012407–012411 (2009).
- 480 53. Läuchli, A., Mila, F. & Penc, K. Quadrupolar phases of the  $s=1$  bilinear-biquadratic heisen-  
481 berg model on the triangular lattice. *Phys. Rev. Lett.* **97**, 087205–087209 (2006).

- 482 54. Barbeau, M. M. S., Eckstein, M., Katsnelson, M. I. & Mentink, J. H. Optical control of com-  
483 peting exchange interactions and coherent spin-charge coupling in two-orbital Mott insulators.  
484 *SciPost Phys.* **6**, 27–57 (2019).



Figure 1: **Biquadratic exchange interactions in 2D magnets.** **a**, Diagram of the rotation of spins  $S_i$  and  $S_j$  in the unit cell (defined by vectors  $\mathbf{a}_1$  and  $\mathbf{a}_2$ ) of a 2D magnet by a relative angle  $\theta$  between them. Spins are rotated symmetrically in opposite directions from  $0^\circ$  to  $180^\circ$ . **b-e**, Relative total energy (eV) as a function of  $\theta(^\circ)$  for different monolayers of 2D magnets: trihalides ( $\text{CrX}_3$ ,  $\text{X}=\text{F, Cl, Br, I}$ ), metal tribromides ( $\text{MBr}_3$ ,  $\text{M}=\text{Mn, Cu, Fe, V}$ ), chromium based ternary tellurides ( $\text{Cr}_2\text{X}_2\text{Te}_6$ ,  $\text{X}=\text{Ge, P, Si}$ ), manganese based ternary chalcogenides ( $\text{Mn}_2\text{P}_2\text{X}_6$ ,  $\text{X}=\text{S, Se, Te}$ ), transition metal dichalcogenides ( $\text{MnX}_2$ ,  $\text{X}=\text{S, Se, Te}$ ) of different phases ( $2H$ ,  $1T$ ) and an iron-based dichalcogenide ( $2H\text{-FeS}_2$ ). The reference energy is taken at  $0^\circ$  as the spins oriented at the same direction. Rotations can occur in-plane or out-of-plane with similar behavior. Symbols are calculated energies. Dashed lines correspond to a quadratic fitting using  $E_{bq}^{tot}(\theta) = A_0^{bq} + A_1^{bq} \cdot S^2 \cos(\theta) + A_2^{bq} \cdot S^4 \cos^2(\theta)$ , while color filling areas indicate the deviation between the quadratic  $E_{bq}^{tot}$  and a linear fitting using  $E_{bl}^{tot}(\theta) = A_0^{bl} + A_1^{bl} \cdot S^2 \cos(\theta)$ . Materials that show large deviation, such as  $\text{CuBr}_3$  or  $2H\text{-FeS}_2$ , develop large BQ exchange interactions. **f**, Logarithm of the total energies (DFT) for the dataset in **b-e**, as a function of  $\theta$ . Data analytics using polynomial regression (least-squares algorithm) in terms of linear ( $Q^1$ ), quadratic ( $Q^2$ ) and cubic ( $Q^3$ ) approaches is evaluated over the calculated DFT energies (dots).



Figure 2: **Bilinear (BL) and biquadratic (BQ) exchange interactions in 2D magnets.** **a**, Schematic of the BL exchanges at first ( $J_1$ ), second ( $J_2$ ) and third ( $J_3$ ) nearest neighbors (NN), and BQ exchange ( $K_{bq}$ ) at first NN. Single and double line diagrams represent BL and BQ exchanges, respectively. The two inequivalent magnetic sites in the honeycomb lattice are shown by faint blue ( $M_A$ ) and faint red ( $M_B$ ) dots. The blue orbits inside of the hexagons represent the magnetic flux  $\phi$  generated by the second-NN Dzyaloshinskii-Moriya interactions (DMI), which breaks the inversion symmetry of the lattice. The dashed lines show the magnon hopping between second NN as the magnons gain a phase given by  $\phi$  (see text). The lattice vectors  $\mathbf{u}_i$  ( $i = 1, 2$ ) and  $\tau_j$  ( $i = 1, 2, 3$ ) show the first and second NN on the lattice, respectively. **b**, Zoom-in on the BQ exchange process involving two electrons between sites  $M_A$  and  $M_B$  with  $3d^m$  electrons in the valence. The BQ exchange  $K_{bq}$  is mediated by non-magnetic atoms X with a valence given by  $np$  electrons, where  $n$  will depend on the atomic elements involved. An on-site Hubbard  $U$  term is at the  $M_{A,B}$  sites with  $U_{ex}$  representing the potential spin-splitting when the spins of the electrons involved in the BQ exchange align ferro- or anti-ferromagnetically (Supplementary Section ). The difference between up and down spin coupling is given by  $2U_{ex}$ . **c**,  $K_{bq}/J_{bl}$  versus  $\Delta_0$ (eV) for all materials displaying BQ exchange interactions. Magnetic atoms with similar chemical environment in terms of Coulomb repulsion, exchange interactions and valence follow alike behavior for  $K_{bq}/J_{bl}$ . For instance, Cr in blue and Mn in green (inset). Orange dots show materials with dissimilar electronic configurations but with  $\Delta_0 = 0$ .

Figure 3: **Monte-Carlo simulations at different levels of theory including BL and BQ exchange interactions. a-b** Magnetization ( $M/M_0$ ) and logarithm of the magnetic longitudinal susceptibility  $\ln\chi_m$  (a.u.) versus temperature (K), respectively, for monolayer  $\text{CrI}_3$ . Calculated and fitting curves using  $M/M_0 = (1 - T/T_c)^\beta$  (where  $T_c$  and  $\beta$  are the critical temperature and coefficient, respectively) are shown by dots and solid lines, respectively, in **a**. Solid lines in **b** show the interpolation between points. Different curves correspond to different number of NN, from one up to third, taken into account in BL interactions:  $\text{BL}^{1\text{st}}$  (faint red),  $\text{BL}^{1\text{st},2\text{nd},3\text{rd}}$  (faint blue). Results including BQ exchange at first NN ( $\text{BQ}^{1\text{st}}$ ) with different number of BL exchanges are shown in purple ( $\text{BL}^{1\text{st}} + \text{BQ}^{1\text{st}}$ ) and faint green ( $\text{BL}^{1\text{st},2\text{nd},3\text{rd}} + \text{BQ}^{1\text{st}}$ ). Critical temperatures ( $T_c$ ) at each level of BL and BQ exchange interactions are indicated at **b** with the maximum magnitude of  $\ln\chi_m$  (a.u.) highlighted. Magnetic susceptibility is shown in logarithm scale for clarify. Experimental critical temperature ( $T_c^{\text{exp}}$ ) is included for comparison. **c-d**, and **e-f**, similar plots as in **a-b**, for  $\text{CrBr}_3$  and  $\text{CrCl}_3$ , respectively. Critical exponents  $\beta$  extracted from the simulations for  $\text{BL}^{1\text{st},2\text{nd},3\text{rd}} + \text{BQ}^{1\text{st}}$  are  $\beta = 0.22, 0.24$  and  $0.28$  for  $\text{CrI}_3, \text{CrBr}_3$  and  $\text{CrCl}_3$  respectively. Magnitudes of  $\beta$  for  $\text{BL}^{1\text{st},2\text{nd},3\text{rd}}$  are  $0.25, 0.28$  and  $0.32$  for  $\text{CrI}_3, \text{CrBr}_3$  and  $\text{CrCl}_3$  respectively.

Figure 4: **Magnon spectra  $\omega(\text{meV})$  at different levels of theory for monolayer  $\text{CrI}_3$ .** **a**,  $\omega(\text{meV})$  versus  $\mathbf{k}$  at the first Brillouin zone ( $\Gamma - K - M - K - \Gamma$ ) using a XXZ model.  $J_1$  varies within  $0 - 3.50$  meV in steps of  $0.5$  meV from each curve (color map). **b**, Similar as **a**, but with a fixed  $J_1 = 2.01$  meV and varying  $J_2$  within  $0 - 0.30$  meV (color map) in steps of  $0.05$  meV. **c-e**,  $\omega(\text{meV})$  versus  $\mathbf{k}$  for different models: XXZ including BQ exchange (XXZ+BQ), XXZ including DMI (XXZ+DMI), and XXZ including both BQ exchange and DMI (XXX+BQ+DMI). In these plots,  $J_1 = 2.01$  meV,  $K_{bq} = 0.22$  (on **c** and **e**),  $A_z = 0.31$  meV<sup>41</sup> (on **d** and **e**) and  $J_2$  varies within  $0 - 0.30$  meV. **f**, Comparison between the XXZ+BQ+DMI model and the experimental data<sup>41</sup> recently measured for bulk  $\text{CrI}_3$ . We used as parameters:  $J_1 = 1.01$  meV,  $J_2 = 0.10$  meV,  $K_{bq} = 0.22$  meV and  $A_z = 0.31$  meV<sup>41</sup>.



Material	$\mu_M$ ( $\mu_B$ )	S	$K_{bq}$ (meV)
CrI <sub>3</sub>	3.36	1.5	0.21
CrBr <sub>3</sub>	3.17	1.5	0.22
CrCl <sub>3</sub>	3.05	1.5	0.21
CrF <sub>3</sub>	2.94	1.5	0.09
MnBr <sub>3</sub>	3.88	2	0.04
CuBr <sub>3</sub>	0.53	1	39.16
FeBr <sub>3</sub>	3.88	2	0.06
VBr <sub>3</sub>	1.93	1	2.85
CrGeTe <sub>3</sub>	2.81	1.5	0.35
CrPTe <sub>3</sub>	2.92	1.5	0.35
CrSiTe <sub>3</sub>	3.13	1.5	0.31
MnPS <sub>3</sub>	4.24	2	0.02
MnPSe <sub>3</sub>	4.21	2	0.02
MnPTe <sub>3</sub>	3.93	2	0.11
1T-MnSe <sub>2</sub>	3.49	1.5	0.74
2H-MnSe <sub>2</sub>	3.49	2	0.15
1T-MnTe <sub>2</sub>	3.71	2	0.14
2H-MnTe <sub>2</sub>	3.78	2	0.10
1T-MnS <sub>2</sub>	3.28	1.5	1.09
2H-MnS <sub>2</sub>	3.27	1.5	1.55
2H-FeS <sub>2</sub>	2.18	1	20.11

Table 1: Calculated biquadratic exchange ( $K_{bq}$ ) for several 2D magnetic materials with honeycomb (faint blue) and hexagonal (faint red) lattices using non-collinear ab initio methods as explained in the text. The magnitudes of the spin angular momentum ( $S$ ) used in the model (Supplementary Section ) and the magnetic moments at the metal atoms ( $\mu_M$ ) are also included.

Comp.	$J_1$ (meV)	$J_2$ ( $\mu$ eV)	$J_3$ ( $\mu$ eV)	$\lambda_1$ ( $\mu$ eV)	$\lambda_2$ ( $\mu$ eV)	$\lambda_3$ ( $\mu$ eV)	$D$ ( $\mu$ eV)
CrI <sub>3</sub>	2.01	320.02	8.10	106.8	-10.24	0.91	108.82
CrBr <sub>3</sub>	1.66	164.35	-11.60	20.69	-2.06	-0.69	34.09
CrCl <sub>3</sub>	1.28	72.03	-25.18	20.07	-9.74	-0.51	12.67
CrF <sub>3</sub>	-0.23	17.27	0.20	3.33	-0.67	-0.14	122.02

Table 2: Computed values of several magnetic quantities for CrX<sub>3</sub> (X=I, Br, Cl, F) at different number of nearest neighbors: isotropic ( $J_1$ ,  $J_2$ ,  $J_3$ ) and anisotropic ( $\lambda_1$ ,  $\lambda_2$ ,  $\lambda_3$ ) BL exchanges. The on-site magnetic anisotropy  $D$  is also included. See Supplementary Section for details.



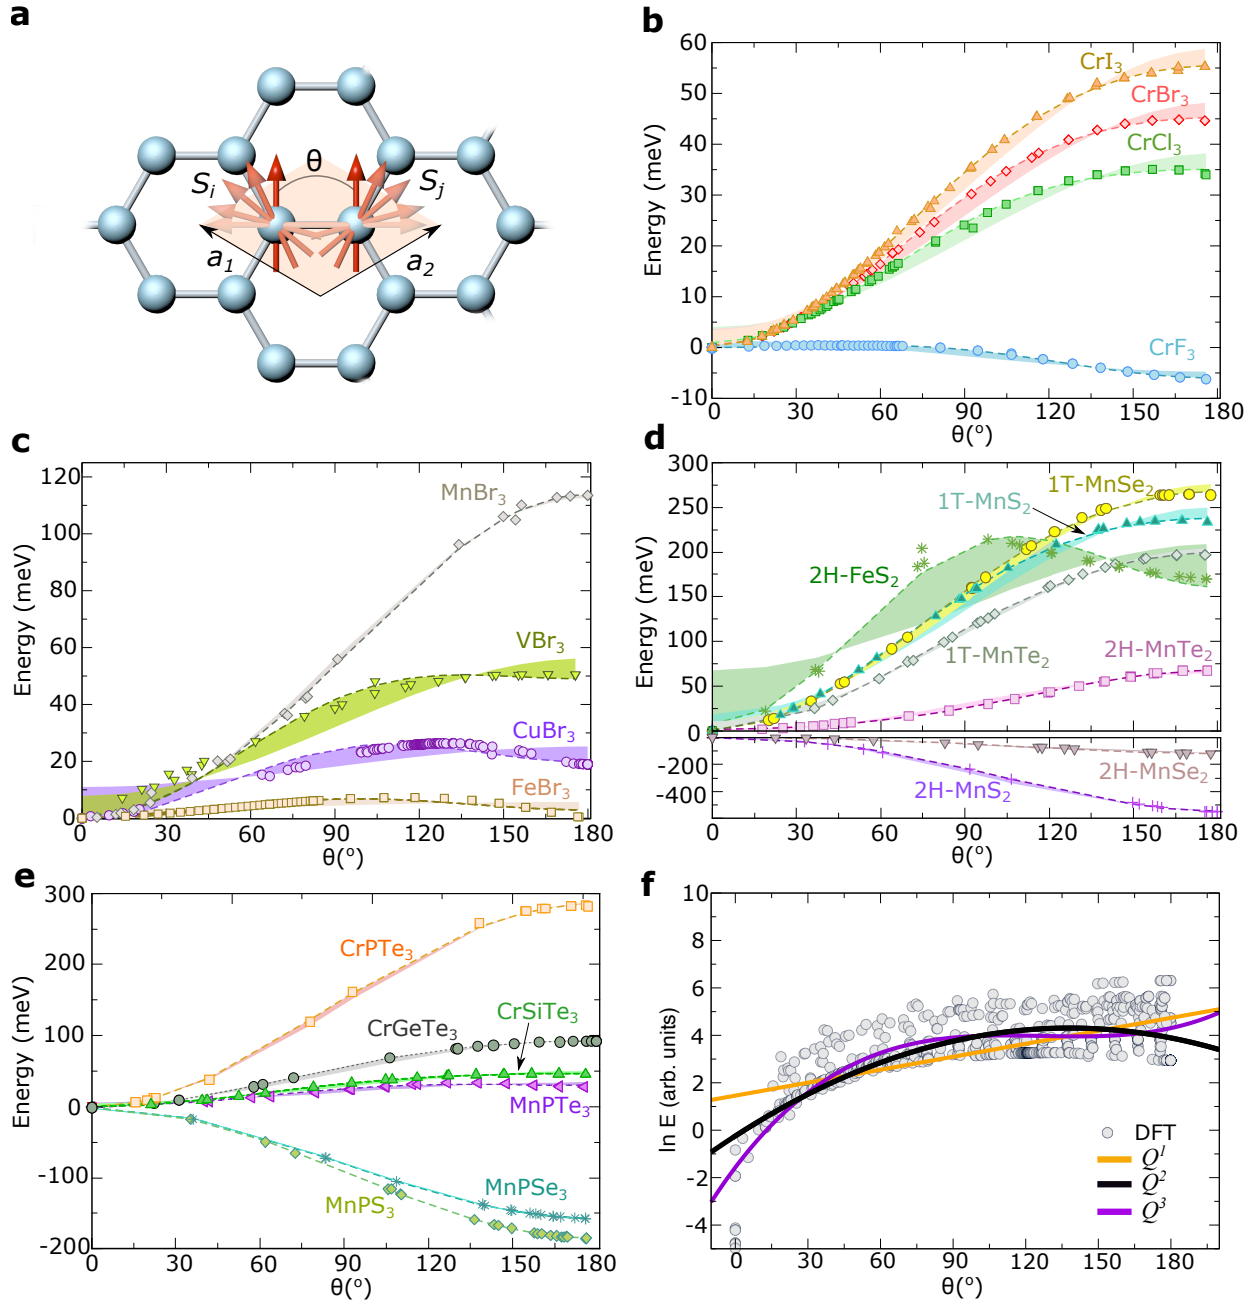


Figure 1:



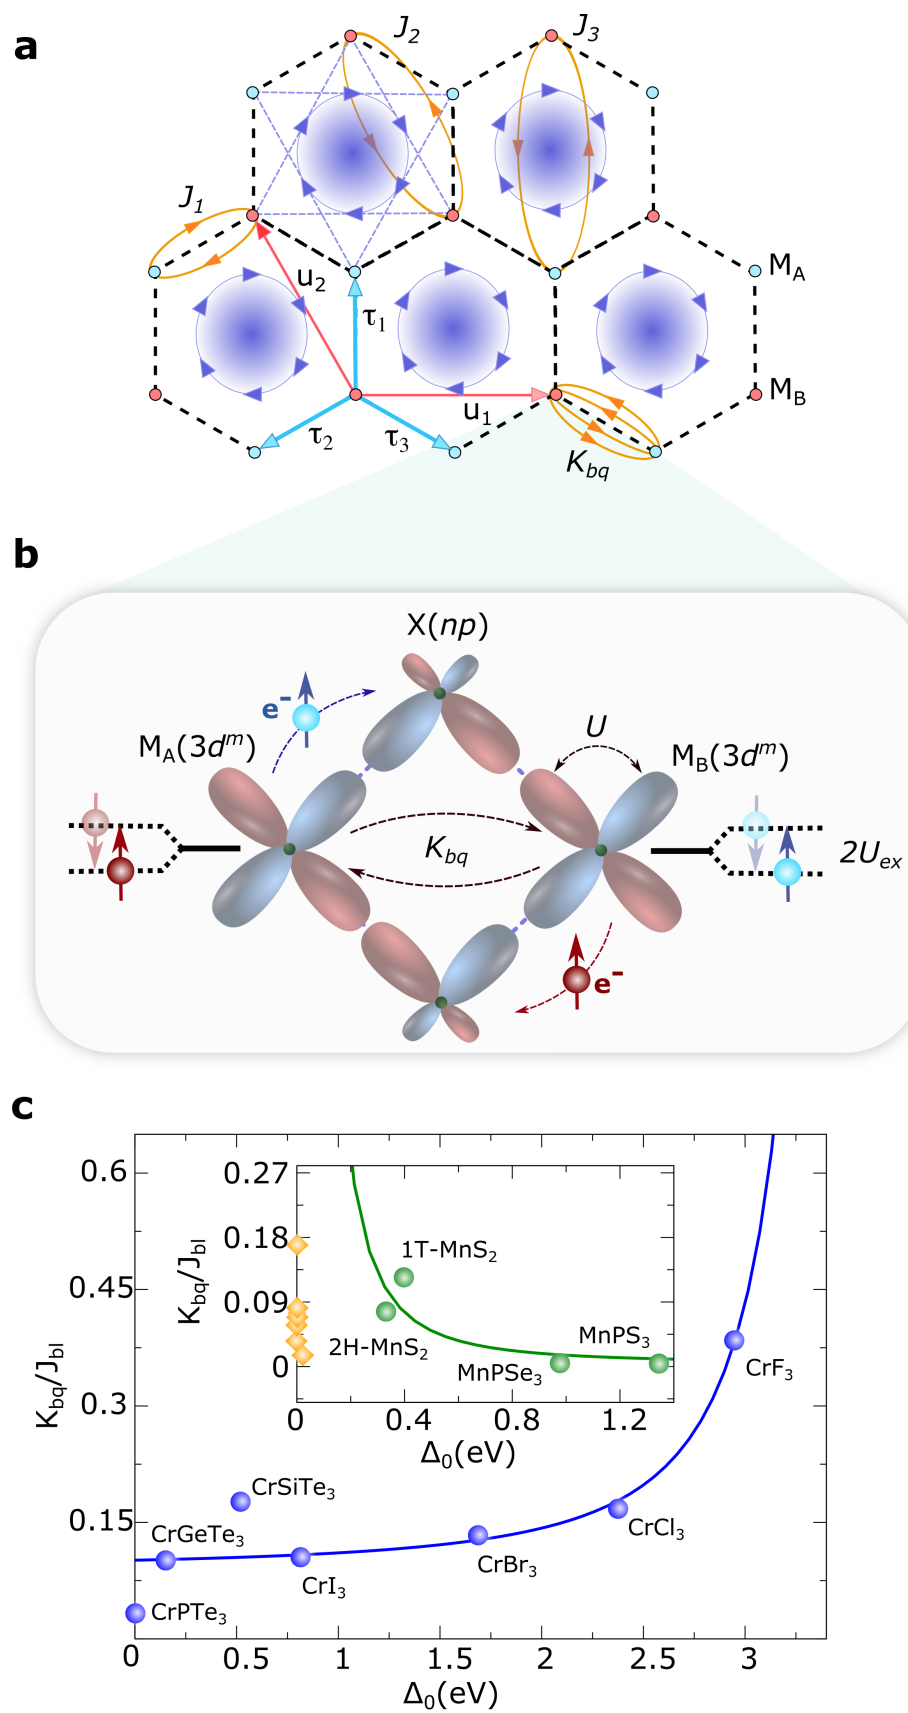


Figure 2:

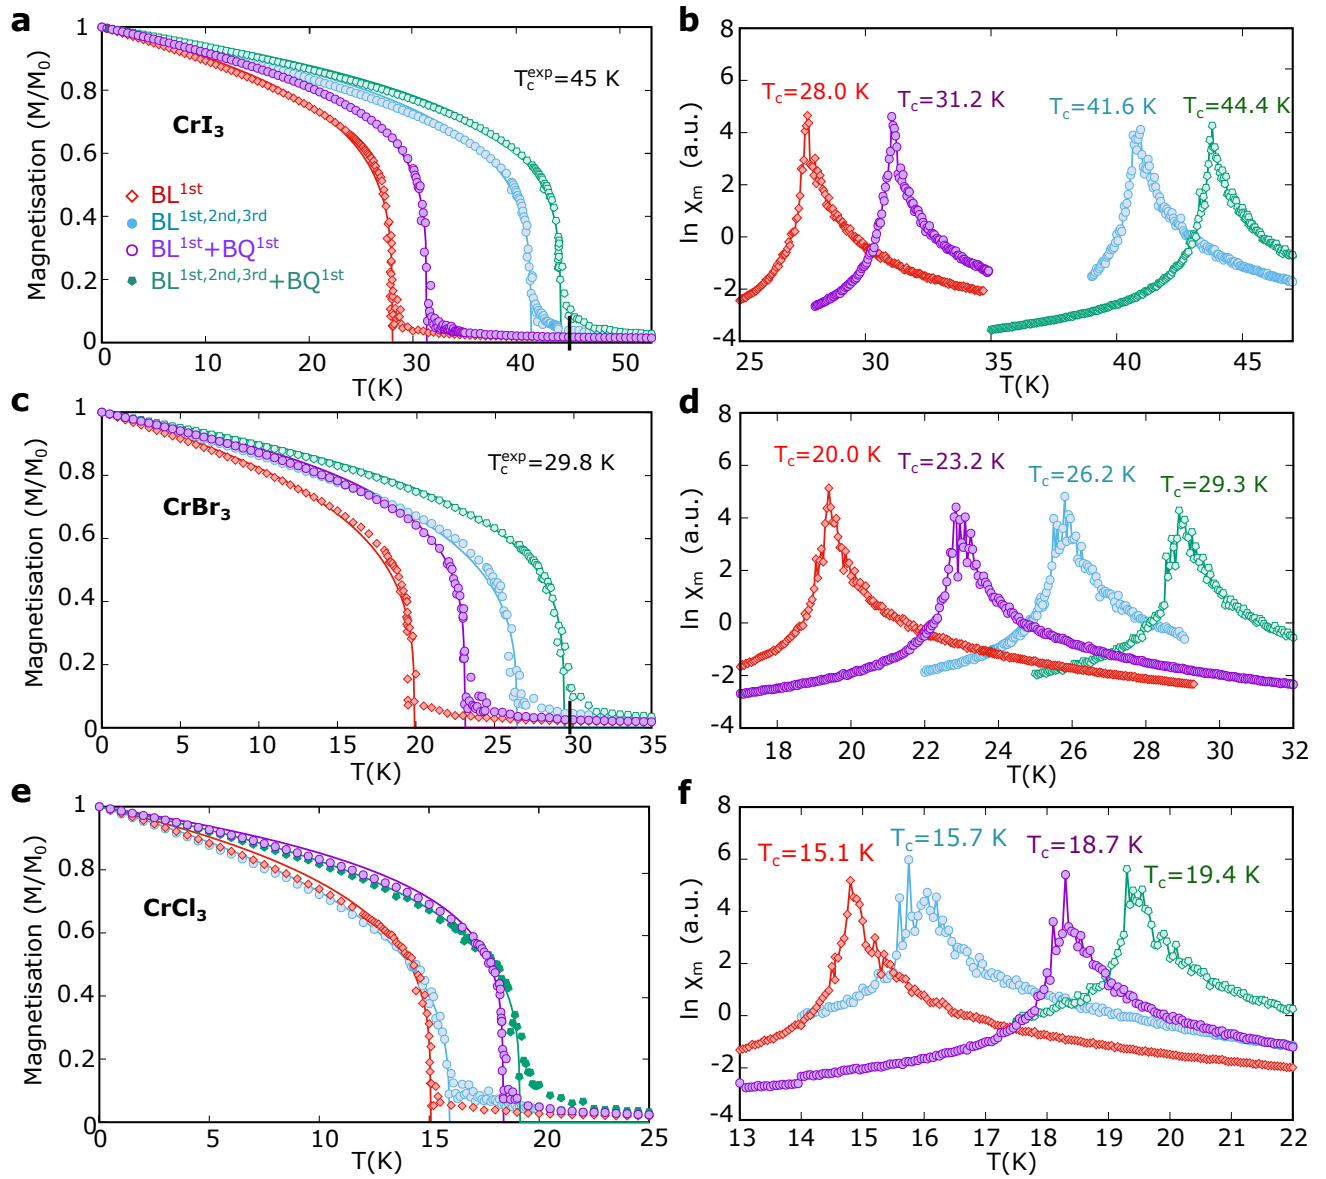


Figure 3:

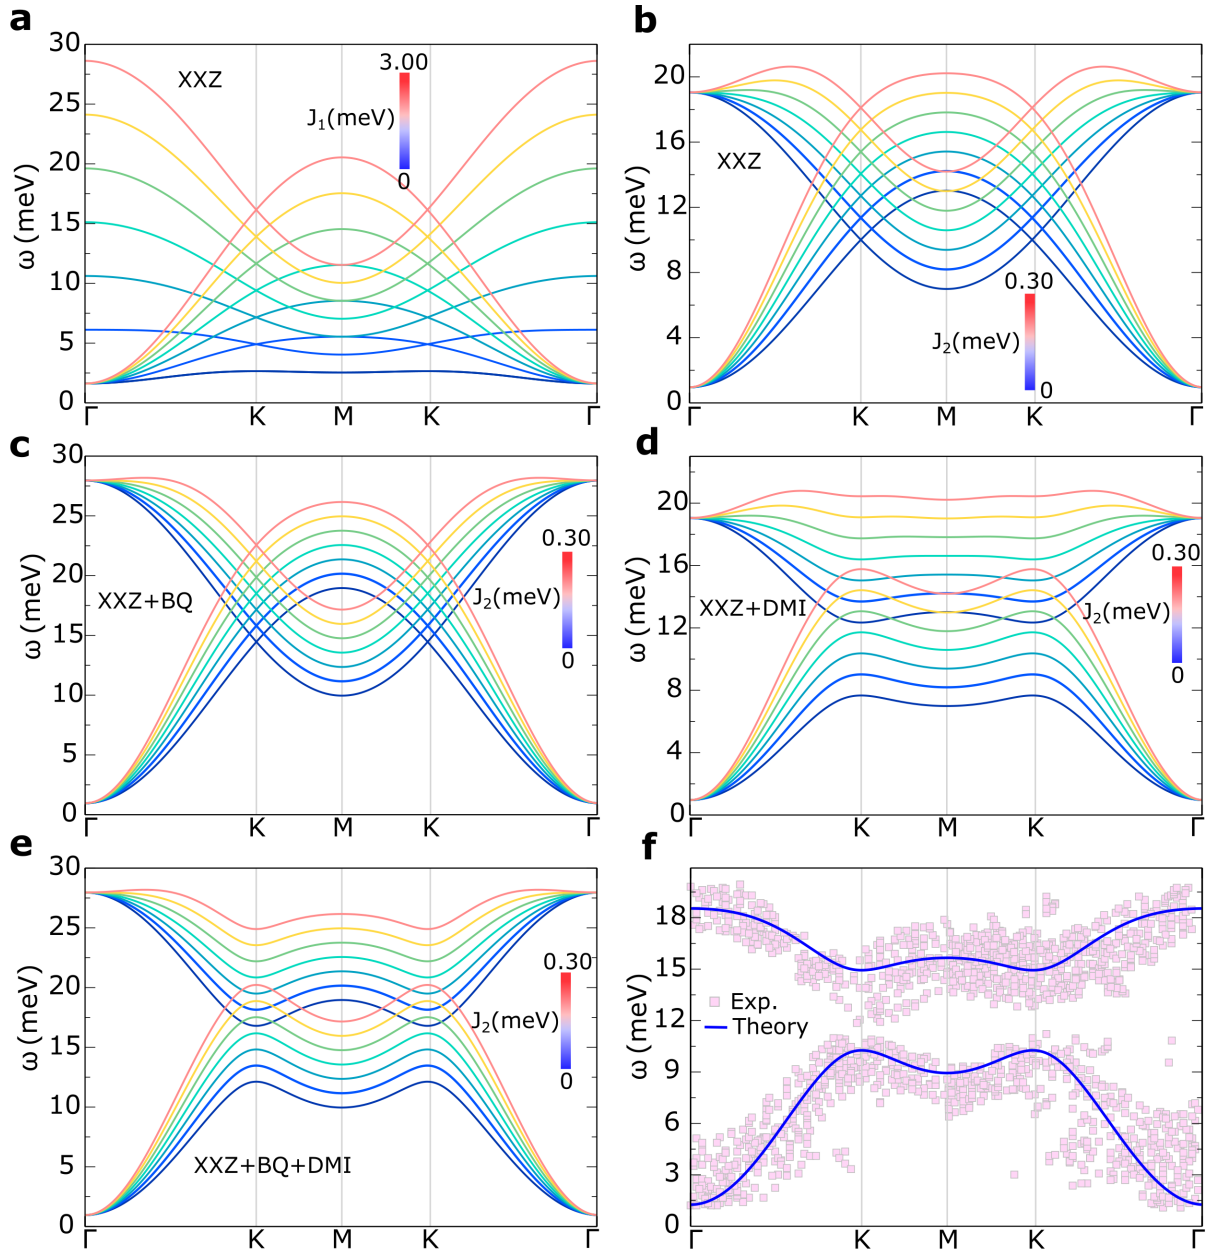


Figure 4: